

Fiber Optics
Dr. Vipul Rastogi
Department of Physics
Indian Institute of Technology, Roorkee

Lecture – 34
Optical Sources and Detectors – II

Let us continue our discussion on semiconductors and semiconductor based optical sources in this lecture. So, what we were discussing was the probability of occupancy of an energy state, which is given by a function which is known as Fermi function is defined as $f(E)$ is equal to 1 over 1 plus exponential $(E - E_f)$ over $k_B T$.

(Refer Slide Time: 00:30)

Probability of occupancy of an energy state

At $T = 0$ K

- all electrons occupy the lowest possible energy state
- the valence band is completely filled
- the conduction band is completely empty

At elevated temperatures

- some electrons from valence band are thermally excited to conduction band
- some states in the conduction band are occupied
- correspondingly some empty states in the valence band are created


Probability of occupation of an energy state E is given by Fermi function

$$f(E) = \frac{1}{1 + \exp\left(\frac{E - E_f}{k_B T}\right)}$$

BIT ROORKEE NPTEL ONLINE CERTIFICATION COURSE 2

Let us look at intrinsic semiconductor and the probability of occupation of energy states in an intrinsic semiconductor.

(Refer Slide Time: 00:49)

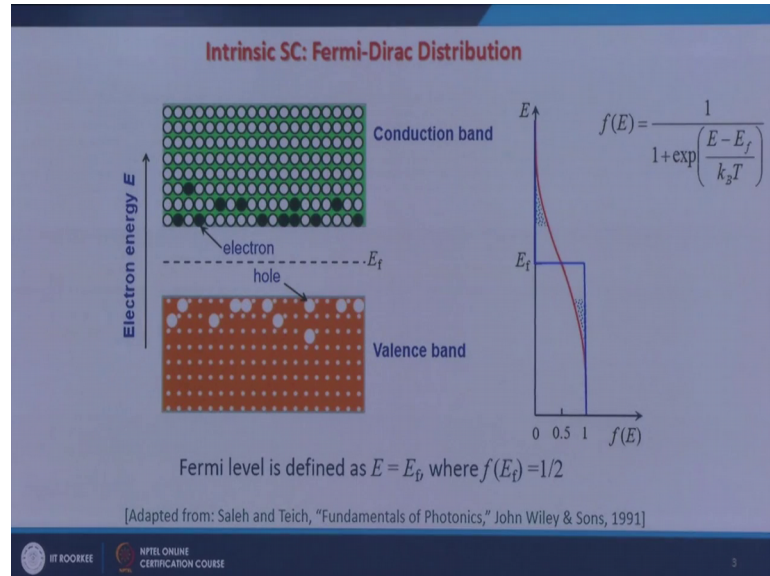


This kind of distribution is defined by this Fermi function is known as Fermi Dirac a statistical distribution. So, in an intrinsic semiconductor I have valence band and I have conduction band, then at absolute 0 I know that valence band is completely filled and the conduction band is completely empty. That is the probability of occupation of energy states here in the valence band is 1 while the probability of occupation of energy states in conduction band is 0. So, if I look at this function and I put t is equal to 0 here then for e smaller than E f, what I have this is as 1 plus e to the power minus infinity. So, f E is equal to 1. So, I have the probability of occupation 1. While for energies larger than E f I have this because of t is equal to 0 this becomes infinity. So, f E is equal to 0. So, what I see that at absolute 0 up to this level the probability of occupation is 1 while above this level the probability of occupation is nil.

At elevated temperature what happens some of the electrons go here. So, there are some states which are occupied by the electrons, then and there are some vacancies created here. So, the probability of occupation in the valence band goes down a little, and the probability of occupation in the conduction band increases from 0. At E is equal to E f; however, what I find that it is E to the power 0. So, 1 over 2 it is half. So, I define Fermi level as e is equal to E f where f E f is half, f at e is equal to E f is half that is at some

finite temperature t the level which has 50 percent probability of occupation it is a Fermi level, and at absolute 0 the level up to which the probability of occupation is one.

And above which the probability of occupation is nil. So, this is known as Fermi level. In an intrinsic case semiconductor the Fermi level lies in the middle of the gap. If I have n type semiconductor then there are large number of electrons here. So, large number of states are occupied here. So, the Fermi level shifts up; correspondingly the Fermi Dirac distribution looks like this, you have more electron states occupied here. So, you have a larger value of $f E$ here. While in p type semiconductor you have large number of holes here. So, the Fermi level shifts down. Now if you make a junction using this p type material and n type material then what happens is this.

(Refer Slide Time: 05:16)

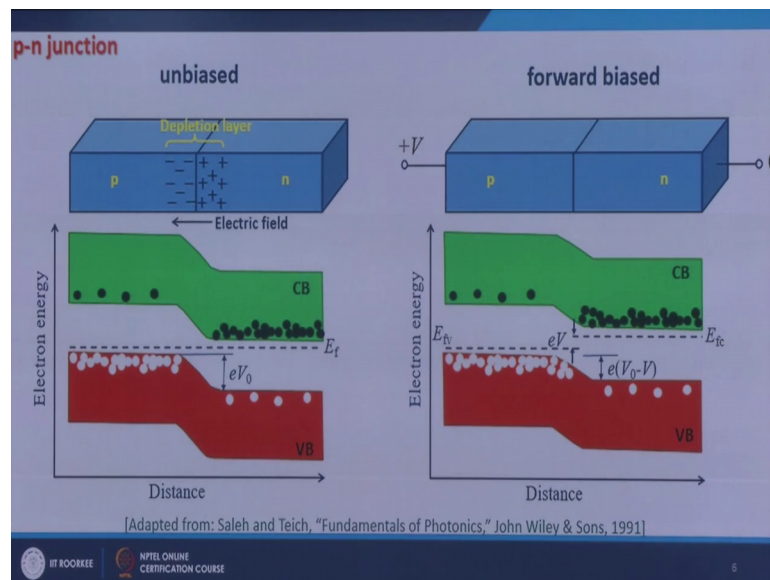

When you join them together then you know in n type you have electrons excess carrier as electrons, which are around the positive ion core and the holes in excess which are around the negative ion core. When you join them together then electrons from here will move towards the p side and will recombine with holes fill the vacancy and will leave behind the positive ion core while here they will combine the hole. So, they will leave behind these negative ions, and this will happen on until an equilibrium is reached.


So, in equilibrium position near the junction I have positive ions on this side and negative ions on this side this sets up an electric field from n to p, this electric field creates a potential energy which looks like this. So, this is the electric potential; if I plot

here the energy of the electron as a function of distance, now what happens is that in equilibrium you see in n type your E_f is near the conduction band, and in p type your E_f is near the valence band. When equilibrium is reached then this E_f is somewhere here and there is banding of this. So, this shifts downwards this shift upwards and there is a potential created here because of this electric field.

So, what happens is that this potential or this electric field prevents electrons going from here to there, and holds from here to there. Remember that this is electron energy that is energy of electron is increasing in this direction, correspondingly the energy of hole is increasing in this direction. So, this is a barrier for electrons and this is a barrier for holes. So, you have a potential barrier created here and the height of the barrier is $e\phi$. If you forward bias it that is if you apply the positive field here.


So, a positive potential here and 0 or negative potential here then you are basically decreasing this potential barrier. Then electrons some of the electrons can now flow from here to the from n type to the p type, and holes can flow from p type to the n to n type and there would be conduction. So, this is forward bias p-n junction. If you reverse bias it that is if this is negative and this is positive then you will further enhance this, and there would be no current flowing in the circuit or very small current will be flowing in the circuit.

(Refer Slide Time: 08:43)

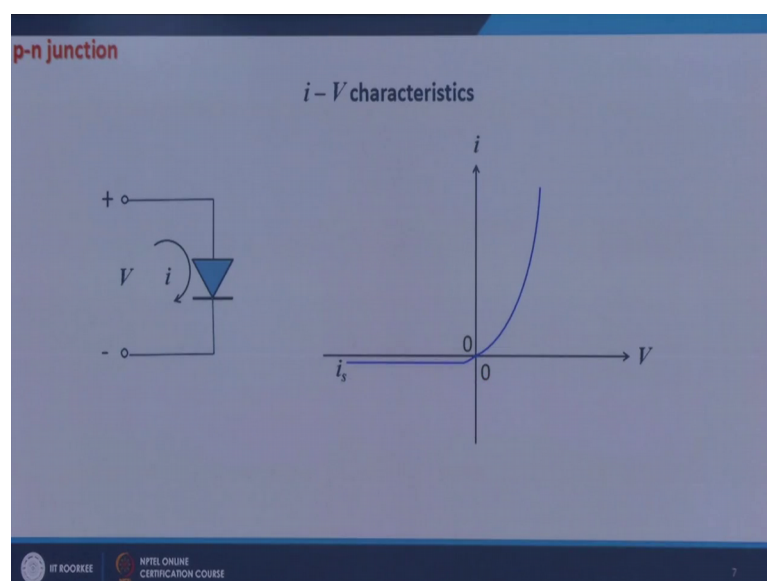

So, if you look at the i v characteristics of a p-n junction. So, in forward bias if you increase the voltage the forward current will increase; however, if you apply the negative voltage and increase this then you will have a reverse saturation current flowing very small in amount and if you apply very large voltage then there would be breakdown.

(Refer Slide Time: 09:13)

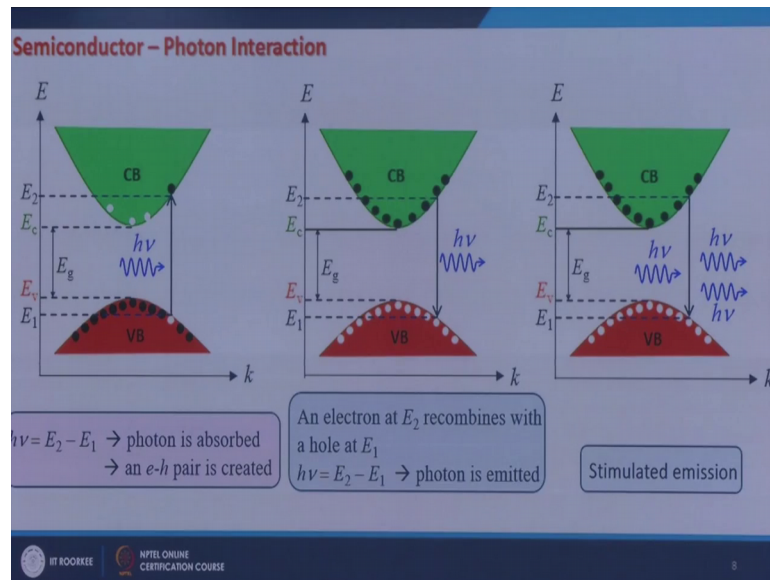

The important thing now, is to understand how photons interact with semiconductors because this will form the basis of our optical sources and optical detectors right. So, if I have a semiconductor which has got valence band and conduction band, there are large number of electrons available here and there are states available here in conduction band for electrons. Now if a photon interacts with this semiconductor and the energy of the photon is such that it is the difference of an energy state here and an energy state available here, then this electron in this energy state will absorb this energy of the photon and will go to this state in this conduction band.


In this way it will leave it will leave behind a vacancy here and an energy state here is occupied. So, in this way it will create an electron hole payer; a photon would be absorbed if the energy is larger than the bandgap then only it will be absorbed. So, absorption of a photon by a semiconductor will create an electron hole payer, and this electron here and hole here can now contribute towards conduction if you apply an appropriate electric field. So, such kind of interaction is responsible for photo detection process to make photo detectors. there is another way in which there can be interaction

between a semiconductor and a photon, and that is if some electrons are already there in conduction band that is the states here are occupied, and holes are available in the valence band the vacancies are there in the valence band, then there is a natural tendency of electrons to go back to the lowest energy state to the lower state.

So, an electron can go from here to the valence band and recombine with hole, and it can do it at its own spontaneously, if the lifetime of these states is very small. Then there would be recombination between electron and hole spontaneously, and as a result of photon of energy difference between these two states will be emitted. This kind of emission of photon is known as spontaneous emission, this process is responsible for light generation in light emitting diodes.

There is another yet another process a process similar to this you already have electrons available in the conduction band and holes in the valence band. So, the electron will recombine with the hole in the valence band, but if the energy states of the electrons here are such that they are long lived they are known as meta stable states. Then this recombination from here to here transition of electron from here to the valence band is triggered by another photon if this transition is triggered by another photon, then the emitted photon is in the same phase and in the same direction as the triggering one, then this kind of emission is known as stimulated emission, this emission is responsible for light generation in lasers.


(Refer Slide Time: 13:58)

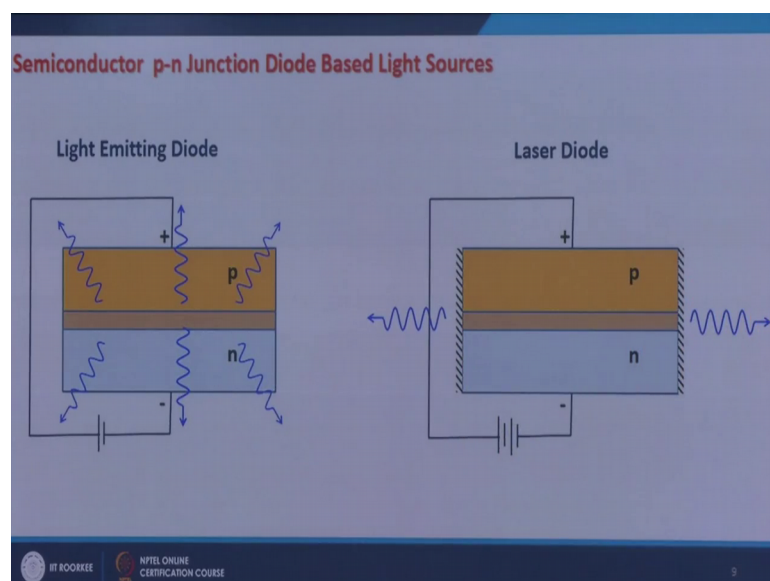

So, we have semiconductor p-n junction diode based light sources is light emitting diode where the light generation is via the process of spontaneous emission. So, what you do you forward bias a p-n junction diode by forward biasing it, you are basically injecting the carriers that is electrons in the conduction band and holes in the valence band. So, since you have now electrons available in conduction band and holes in the valence band.

So, this recombination of them is in is spontaneous manner will give you light output, and this light is incoherent and this is the process responsible for generation of light in light emitting diodes. However, if the light emission is via the process of stimulated emission, then you amplify the radiation and if you place two mirrors here and provide feedback in the K B T, then you can make it a laser from amplifier you can make the oscillator and that is basically a laser. So, this is the process responsible for light generation in laser diodes. So, let us now look at light emitting diodes. So, these are various forms of light emitting diodes available commercially available, the process responsible here for light emission is injection electroluminescence.

(Refer Slide Time: 15:39)

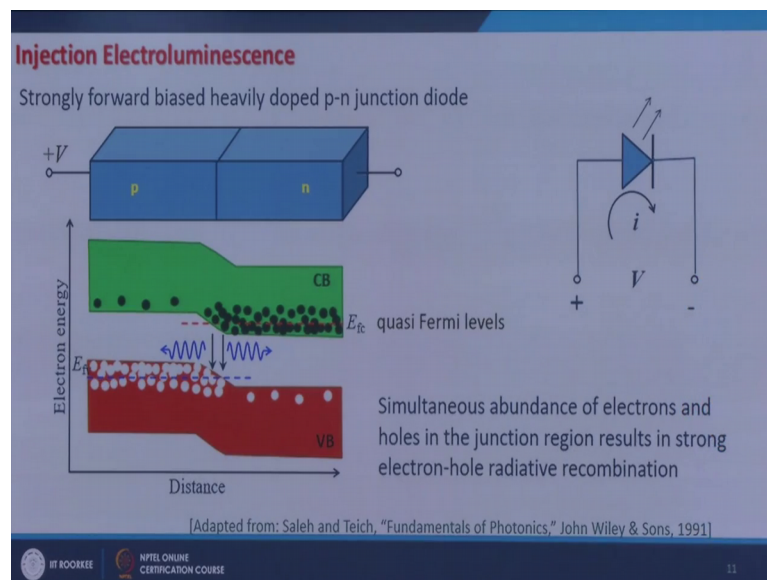

So, I explain this with the help of a strongly forward biased heavily doped p-n junction diode. So, if this p-n junction is heavily doped, then there are large number of electrons in the conduction band and large number of holes in the valence band such that this

Fermi level goes even inside the conduction band and this Fermi level shifts to inside the valence band and these are known as quasi Fermi levels.

The consequence of this heavy doping and strong forward bias is that we are injecting lot of carriers, and lot of carriers are available here now. So, if I look at in the junction region then in the junction region there is simultaneous abundance of electrons and holes. Then these electrons will make transitions will recombine with holes and give you light output. Photons coming out light radiation and in this way an LED will work LED will emit light.

So, if you have a p-n junction diode you forward bias it and you get light out of it. A very important parameter of a light emitting diode is its efficiency quantum efficiency, how efficient it is in generation of light. To understand this let us go back to the very basic phenomenon of light emission in such devices, I have just seen that light is emitted by radiative recombination of electrons and holes. So, electron is in the conduction band hole is in the valence band, electron recombines with hole there is a radiative recombination. So, photon comes out, but this electron can recombine with hole.

By another process also, that is by releasing heat by releasing thermal energy instead of releasing the photon such kind of combination is known as non radiative recombination. So, I now have two kinds of recombinations one is radiative recombination where photon comes out, another is non radiative recombination where the energy is released in the form of thermal energy. But I know that light is generated by the process of radiative recombination. So, when I inject current in a p-n junction, I create electron hole payers then not all the electron hole payers recombine radiatively, some of them are recombined non radiatively, and this gives me some finite quantum efficiency, because some part is lost in heating up the device.

(Refer Slide Time: 19:13)

Quantum Efficiency

Electron – hole pairs are created in the junction region by current injection

Light emission : due to radiative recombination of electrons and holes

Electrons and holes can also recombine in a non-radiative fashion

Non-radiative recombination results in loss of energy in the form of heat

- not all the injection current is converted into light
- some part is lost in heating up the device
- Finite quantum efficiency of the LED

BIT BOORKEE NPTEL ONLINE CERTIFICATION COURSE 12

So, it will give me finite quantum efficiency of the LED I cannot have 100 percent quantum efficiency in an LED in such a way. So, to work out the expression for quantum efficiency, let us look at the carrier concentration how the carrier concentration decreases with time because electrons recombine with holes. So, the number of electrons decrease in the conduction band and number of holes decrease in the valence band.

(Refer Slide Time: 19:58)

Quantum Efficiency

Carrier concentration decreases with time according to $n = n_0 e^{-t/\tau}$

Rate of decrease of carrier concentration $\frac{dn}{dt} = -\frac{n_0}{\tau} e^{-t/\tau} = -\frac{n}{\tau}$

= total recombination rate (radiative + nonradiative)
 $\tau \rightarrow$ total recombination life time

<u>Radiative Recombination Rate</u>	<u>Non-radiative Recombination Rate</u>
$R_r = \frac{n}{\tau_r}$	$R_{nr} = \frac{n}{\tau_{nr}}$
$\tau_r \rightarrow$ radiative recombination life time	$\tau_{nr} \rightarrow$ non-radiative recombination life time

BIT BOORKEE NPTEL ONLINE CERTIFICATION COURSE 13

So, the number of carriers decrease according to n is equal to $n_0 e^{-t/\tau}$, where n_0 is the number of carriers at t is equal to 0, this τ is known as

lifetime. I can find out from here what is the rate of decrease of carrier concentration by simply doing $\frac{dn}{dt}$, if I do $\frac{dn}{dt}$ from here then it is $-\frac{n}{\tau}$. Minus simply indicates that the carriers are decreasing.



So, where τ is recombination lifetime and this is total recombination rate it involves radiative as well as non radiative. I do not know which process is responsible here in what proportion, and τ is basically total recombination lifetime. Now if I say that R_r is the rate which is due to radiative recombination, then R_r would be given by $\frac{n}{\tau_r}$. I drop the minus sign because it only indicates the decrease in the number of carriers then R_r is equal to $\frac{n}{\tau_r}$ where τ_r is the radiative recombination lifetime and you can also have decrease in the concentration of carriers by non radiative recombination. So, I define radiative recombination rate as R_{nr} is equal to $\frac{n}{\tau_{nr}}$, where τ_{nr} is the non radiative recombination lifetime.

(Refer Slide Time: 22:09)

Internal quantum efficiency

$$\eta_{int} = \frac{R_r}{R_r + R_{nr}}$$

$$\eta_{int} = \frac{\frac{n}{\tau_r}}{\frac{n}{\tau_r} + \frac{n}{\tau_{nr}}} = \frac{\frac{1}{\tau_r}}{\frac{1}{\tau_r} + \frac{1}{\tau_{nr}}} = \frac{\tau}{\tau + \tau_{nr}}$$



14

So, the internal quantum efficiency I can now calculate because my the light in LED is coming out only because of radiative recombination. So, the internal quantum efficiency is given by η_{int} is equal to R_r divided by R_r plus R_{nr} . That this what fraction of recombinations is via the process of radiative recombination. Since R is equal to $\frac{n}{\tau}$. So, if I put it there. So, I can write it down as τ over τ_r , where τ is the total recombination lifetime and is given by $\frac{1}{\tau}$ is equal to $\frac{1}{\tau_r}$ plus $\frac{1}{\tau_{nr}}$ because r is equal to R_r plus R_{nr} . In general this τ_r and τ_{nr} are comparable for

a direct bandgap semiconductor such as gallium aluminum arsenide or indium gallium arsenide phosphide.

So, if they are comparable then η_{int} is typically 50 percent this is for homo junction LEDs homo junction means the junction between the same material you know p type and n type materials are the same. However, for double hetero junction LED you can increase it up to 80 percent 60 to 80 percent, how much power is generated in the device.

(Refer Slide Time: 23:58)



Internally generated power

Total number of recombinations per second $= R_r + R_{nr}$
 $=$ total number of excess electrons injected per second
 $= \frac{i}{e}$ where, i is the injected current

Number of recombinations per second that result in generation of photons $= \eta_{int} \frac{i}{e}$

Each radiative recombination results in generation of photon of energy $h\nu$

Internally generated power $P_{int} = \eta_{int} \frac{i}{e} h\nu = \eta_{int} \frac{1.24}{\lambda_0 (\mu m)} i$

I know that total number of recombinations per second are R_r plus R_{nr} which is the total recombination rate and this is nothing, but the total number of excess electrons injected per second.

So whatever excess electrons are injected per second they are getting recombined. So, the number of electrons injected per second should be equal to the number of recombinations per second. How many excess electrons are injected per second? Well if i is the current then i/e is the number of electrons injected per second. Now how many of these recombinations result in generation of photons well the fraction, which is corresponding to radiative recombination, and that fraction is η_{int} .

So, the number of recombinations which are radiative are now η_{int} and then the number of recombinations that result in generation of photons would be η_{int} times i/e and each recombination these are the recombinations per second and each

of these recombinations will give you one photon, and I know the energy of one photon is $h\nu$. So, if I multiply this by $h\nu$ I will get the energy per unit time that is power. So, the internally generated power would simply be $\eta_{\text{internal}} \times i$ over e times $h\nu$, and I can convert this into this particular fashion for convenience, because $h\nu$ is equal to hc over λ .

So, your P_{internal} is equal to $\eta_{\text{internal}} \times i$ over e times $h\nu$.

(Refer Slide Time: 26:17)

$$P_{\text{int}} = n_{\text{int}} \frac{i}{e} h\nu$$

$$= n_{\text{int}} \frac{i/hc}{\lambda}$$

$$= n_{\text{int}} \cdot \frac{6.6 \times 10^{-34} \text{ (Js)} \cdot 3 \times 10^8 \text{ (m/s)}}{1.6 \times 10^{-19} \text{ C}}$$

So, this is $\eta_{\text{internal}} \times i$ over e times hc over λ ; if you look at hc over e then h . So, this is simply $\eta_{\text{internal}} \times h$ 6.6 into 10 to the power minus 34 joules second, c is equal to 3 into 10 to the power 8 meter per second, and e is equal to 1.6 into 10 to the power minus 19 coulomb times i over λ . So, this we had worked out previously also. So, this comes out to be 1.24 into 10 to the power minus 6 , and 10 to the power minus 6 I observe as micrometer in λ downstairs. So, you can write it down like this. So, this is the internally generated power.

In the next lecture I would look into some more characteristics of a light emitting diode and I will also look into a laser diode.

Thank you.